

# Machining recommendation

## Duopal XTreme

### Machining of Duopal XTreme panels

#### Introduction

When machining Duopal XTreme by sawing, milling, grooving and boring, ensure that suitable tools and machining parameters are selected. The wrong choice of tools and their conditions of use can lead to beading, unacceptable heating or even melting of the workpiece surface and damage. This machining guideline provides recommendations for the optimum machining of this panel material without claiming to be exhaustive.

#### General machining guidelines

When machining Duopal XTreme panels, the reference values from the table for the selection of the cutting speed ( $v_c$ ) and the tooth feed rate ( $f_z$ ) should be observed, depending on the machining method.

| Machining method | Cutting speed $v_c$ [m/s] |
|------------------|---------------------------|
| Sawing           | 60 - 90                   |
| Hogging          | 60 - 80                   |
| Cutting          | 50 - 70                   |
| Routing          | 10 - 35                   |



| Machining method | Tooth feed rate $f_z$ [mm] |
|------------------|----------------------------|
| Sawing           | 0.02 - 0.12                |
| Hogging          | 0.12 - 0.18                |
| Cutting          | 0.30 - 0.55                |
| Routing          | 0.15 - 0.25                |

These parameters are in relation to the tool diameter (D), number of teeth (Z), RPM (n) and feed speed ( $v_f$ ) used on the processing machine. The right selection of these factors is responsible for a good machining result.

The following formulas apply to the calculation of cutting speed, tooth feed rate and feed speed:

#### $v_c$ – Cutting speed [m/s]

$$v_c = D \cdot \pi \cdot n / 60 \cdot 1000$$

D – Tool diameter [mm]

n – RPM of tool [ $\text{min}^{-1}$ ]

#### $f_z$ – Tooth feed rate [mm]

$$f_z = v_f \cdot n \cdot Z$$

$v_f$  – Feed speed [m/min]

n – RPM of tool [ $\text{min}^{-1}$ ]

Z – Number of teeth

# Machining recommendation

## Duropal XTreme

### **$v_f$ – Tooth feed rate [m/min-1]**

$$v_f = f_z \cdot n \cdot z / 1000$$

$f_z$  – Feed speed [mm]

$n$  – RPM of tool [ $\text{min}^{-1}$ ]

$z$  – Number of teeth

### **Cutting material**

Basically, both tools with carbide cutting edges (HW) and diamond cutting edges (DP diamond polycrystalline) can be used. The use of tools with diamond cutting edges (DP) is recommended in order to extend the tool life at high cutting volume.

# Machining recommendation

## Duropal XTreme

### Cutting the panels with circular sawblades


General note:

- Visible side upwards
- Make sure that the sawblade protrudes correctly (see table)
- Adjust RPM and number of teeth to feed speed
- The use of a scoring sawblade is recommended for precise cuts on the bottom side of the panel

Depending on the sawblade protrusion, the entry and exit angle and thus the quality of the cutting edge change. If the top cutting edge becomes rough, set the circular sawblade higher. If the cut on the bottom side is rough, the circular sawblade must be set lower. In this way the most favourable height setting must be determined.


The following sawblade protrusions ( $\ddot{U}$ ) must be set for sizing and panel sizing saws, depending on the diameter (D):

| Circular sawblade diameter D [mm] | Protrusions $\ddot{U}$ [mm] |
|-----------------------------------|-----------------------------|
| 250                               | ca. 5 - 10                  |
| 300                               |                             |
| 350                               | ca. 8 - 12                  |
| 400                               |                             |
| 450                               | ca. 10 - 15                 |

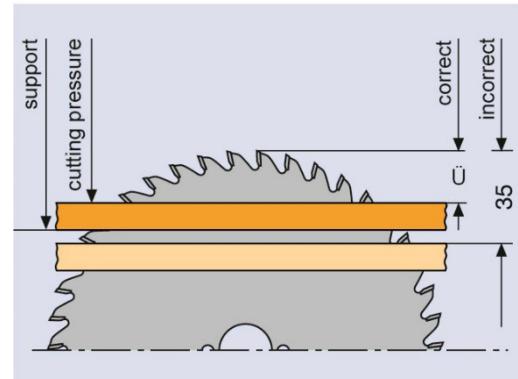

Circular sawblades with a high number of teeth are generally recommended for good machining quality.

For circular sawing, the recommended cutting speed  $v_c$  is 60 - 80 m/s. For diamond-tipped circular sawblades, the cutting speed can be increased up to  $v_c$  90 m/s.



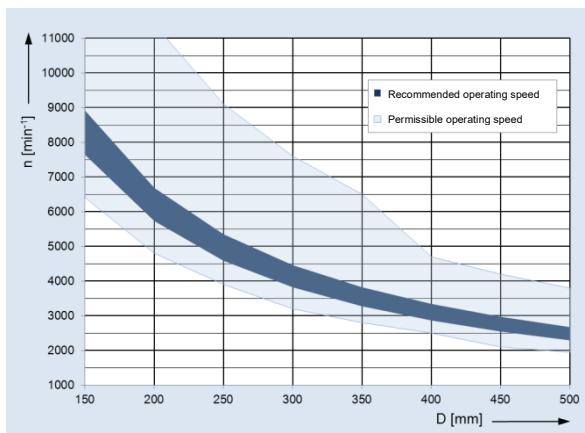


Speed diagram – depending on the circular sawblade diameter

# Machining recommendation

## Duropal XTreme

### Recommended tooth shapes

|   |   |   |   |
|---|---|---|---|
|  |  |  |  |
| FZ/TR<br>(square/trapezoidal teeth)   | HZ/DZ<br>(hollow face/inverted V teeth)   | TR/TR<br>(trapezoidal/trapezoidal teeth)  | WZ/FA<br>(alternating tooth/ bevel)   |

The tooth shapes FZ/TR, HZ/DZ as well as TR/TR are suitable for cutting to size. The tooth shape WZ/FA with special tooth geometry is suitable for sizing when higher quality requirements are placed on the cutting edge.

### Sizing sawblades

Good cutting results and tool life are achieved with the saw tooth shapes HZ/DZ and FZ/TR. With the tooth shape WZ/FA with special tooth geometry, very good cutting results of the cover foil are achieved, but a reduction in tool life must be expected.

### Panel sizing sawblades

With tooth shape TR/TR, good cutting results and tool life are achieved. With tooth shape WZ/FA with special tooth geometry, very good cutting results of the cover foil are achieved, but a reduction in tool life must be expected.


### Sizing saws and panel sizing saws with scoring unit and pressure beam

#### Scoring sawblades


For coated workpieces, the use of a scoring unit is recommended to achieve a good cutting edge quality on the tooth exit side. The cutting width of the scoring sawblade must be set slightly larger than that of the main circular sawblade so that the exiting tooth of the main saw can no longer touch the cutting edge. Since a secure, flat support of the workpieces is only guaranteed with pressure equipment, divided scoring circular sawblades are used on table and sizing saws.

# Machining recommendation

## Duropal XTreme

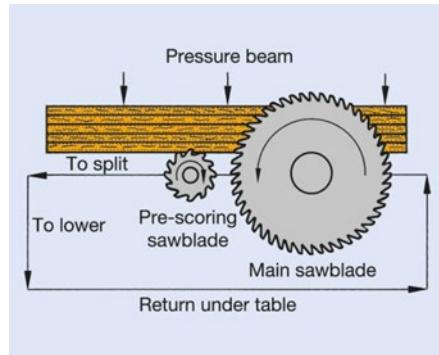

Panel sizing system with scoring unit and pressure device

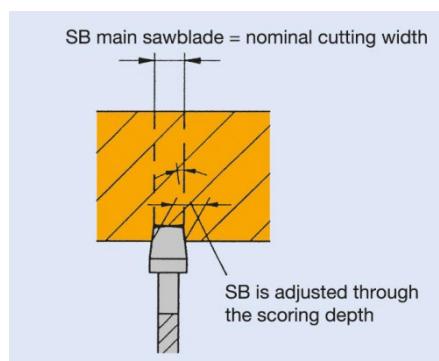

Application diagram of conical scoring sawblade. When maintaining the tools (always in sets), the cutting widths must be matched to each other.

### Circular sawblades for sizing saws and circular table saws (TC-tipped)

The following circular sawblades are suitable for cutting on table and sizing saws.

| D [mm] | SB [mm] | TDI [mm] | BO [mm] | NLA | Z   | ZF    | SW ° | ID     |
|--------|---------|----------|---------|-----|-----|-------|------|--------|
| 250    | 3.2     | 2.2      | 30      | KNL | 80  | FZ/TR | 10   | 163003 |
| 300    | 3.2     | 2.2      | 30      | KNL | 96  | FZ/TR | 10   | 163006 |
| 350    | 3.5     | 2.5      | 30      | KNL | 108 | FZ/TR | 10   | 163008 |
| 220    | 3.2     | 2.2      | 30      | KNL | 42  | HZ/DZ | 10   | 163050 |
| 250    | 3.2     | 2.2      | 30      | KNL | 48  | HZ/DZ | 10   | 163051 |
| 303    | 3.5     | 2.5      | 30      | KNL | 60  | HZ/DZ | 10   | 163052 |
| 350    | 3.5     | 2.5      | 30      | KNL | 72  | HZ/DZ | 10   | 163053 |

Other dimensions available on request

### Circular sawblades for panel sizing saws (TC-tipped)

The following RazorCut PLUS circular sawblades are suitable for cutting on panel sizing saws.

| Machine                    | D [mm] | SB [mm] | TDI [mm] | BO [mm] | NLA                 | Z  | ZF    | SW ° | ID     |
|----------------------------|--------|---------|----------|---------|---------------------|----|-------|------|--------|
|                            | 300    | 4.4     | 3.0      | 30      | KNL                 | 60 | TR/TR | 15   | 161137 |
| Holz-Her, Mayer, Schelling | 350    | 4.4     | 3.2      | 30      | KNL + 2/13/94       | 72 | TR/TR | 15   | 161149 |
| Homag                      | 350    | 4.4     | 3.2      | 60      | 2/14/100            | 72 | TR/TR | 15   | 161150 |
| Giben                      | 350    | 4.4     | 3.2      | 75      | -                   | 72 | TR/TR | 15   | 161151 |
| Selco                      | 355    | 4.4     | 3.2      | 80      | 2/9/130 + 4/19/120  | 72 | TR/TR | 15   | 161153 |
| Giben                      | 380    | 4.4     | 3.2      | 50      | 4/13/80             | 72 | TR/TR | 15   | 161157 |
| Homag                      | 380    | 4.8     | 3.5      | 60      | 2/14/100 + 2/14/125 | 72 | TR/TR | 15   | 161159 |

# Machining recommendation

## Duropal XTreme

| Machine                 | D<br>[mm] | SB<br>[mm] | TDI<br>[mm] | BO<br>[mm] | NLA  | Z  | ZF    | SW<br>° | ID     |
|-------------------------|-----------|------------|-------------|------------|--|----|-------|---------|--------|
| SCM, Gabbiani,<br>Selco | 400       | 4.4        | 3.2         | 80         | 2/14/110 + 2/7/110 + 4/9/100<br>+ 4/19/120 + 2/9/130 | 72 | TR/TR | 15      | 161163 |
| SCM, Gabbiani,<br>Selco | 430       | 4.4        | 3.2         | 80         | 2/14/110 + 2/7/110 + 4/9/100<br>+ 4/19/120 + 2/9/130 | 72 | TR/TR | 15      | 161167 |
| Mayer, Schelling        | 450       | 4.4        | 3.2         | 30         | KNL + 2/13/94  | 72 | TR/TR | 15      | 161168 |
| Homag                   | 450       | 4.8        | 3.5         | 60         | 2/14/125 + 2/19/120                                  | 72 | TR/TR | 15      | 161169 |
| Schelling               | 460       | 4.4        | 3.2         | 30         | 2/13/94  | 72 | TR/TR | 15      | 161170 |

Other dimensions available on request

Panel sizing with circular sawblades is basically to be understood as pre-machining. In order to create an optimal surface for edging and a break-out-free decorative edge, the saw cut must be reworked using a hogger or jointing cutter as described in the next chapter.

### Circular sawblades for cutting HPL laminated panels (approx. 0.8 mm) and coated panels without reworking

With the following BrillianceCut circular sawblades, an optimal finish saw cut of the cover foil is achieved. However, a reduced tool life must be expected. The workpieces produced in this way can be processed directly without an additional work step.

| Machine                        | D<br>[mm] | SB<br>[mm] | TDI<br>[mm] | BO<br>[mm] | NLA                            | Z  | ZF    | SW<br>° | ID     |
|--------------------------------|-----------|------------|-------------|------------|--------------------------------|----|-------|---------|--------|
| Altendorf, Martin,<br>Striebig | 303       | 3.5        | 2.5         | 30         | KNL                            | 60 | TR/TR | 10      | 161028 |
| HolzHer, Panhans,<br>Schelling | 350       | 4.4        | 3.2         | 30         | KNL                            | 72 | WZ/FA | 15      | 161029 |
| Holzma                         | 350       | 4.4        | 3.2         | 60         | 2/14/100                       | 72 | WZ/FA | 15      | 161030 |
| Holzma                         | 380       | 4.8        | 3.5         | 60         | 2/14/100 + 2/14/125 + 2/19/120 | 84 | WZ/FA | 15      | 161031 |
| Panhans, Schelling             | 400       | 4.4        | 3.2         | 30         | KNL                            | 72 | WZ/FA | 15      | 161032 |
| Scheer, Schelling              | 450       | 4.4        | 3.2         | 30         | KNL                            | 72 | WZ/FA | 15      | 161033 |
| Holzma                         | 450       | 4.8        | 3.5         | 60         | 2/14/125 + 2/19/120            | 72 | WZ/FA | 15      | 161034 |

Other dimensions available on request

### For processing worktops with postforming edges

| D<br>[mm] | SB<br>[mm] | TDI<br>[mm] | BO<br>[mm] | NLA    | Z   | ZF        | SW<br>° | ID     |
|-----------|------------|-------------|------------|--------|-----|-----------|---------|--------|
| 303       | 3.2        | 2.6         | 30         | KNL    | 100 | WZ/WZ/FZ  | 10      | 161201 |
| 355       | 3.0        | 2.2         | 30         | KNL    | 120 | WZ/WZ/FZ  | 10      | 161202 |
| 300       | 3.5        | 2.5         | 30         | KNL    | 96  | WZ        | 5       | 163200 |
| 350       | 3.5        | 2.5         | 30         | KNL    | 108 | WZ        | 5       | 163201 |
| 303       | 3.2        | 2.4         | 30         | KNL    | 60  | HZFA/WZFA | 10      | 190698 |
| 350       | 3.2        | 2.4         | 30         | KNL    | 70  | HZFA/WZFA | 10      | 190699 |
| 350       | 3.5        | 2.7         | 30         | 8/6/90 | 110 | WZ/WZ/FZ  | 10      | 161263 |

Other dimensions available on request

# Machining recommendation

## Duropal XTreme

### Jointing on table milling machine or throughfeed systems

Cutterheads with TC turnblade knives or diamond-tipped cutters are always suitable for machining Duropal XTreme panels. In order to create break-out-free edges on the top layers of the panel, jointing tools with an alternating shear angle should be used. The use of jointing cutters with a larger cutting angle ( $>30^\circ$ ) is advantageous. Sizing tools with a higher number of teeth (Z) compared to standard tools tend to provide better cutting quality. Furthermore, ensure a low chip removal between 0.7 to 2.0 mm to reduce tool wear.


Only tools marked "MAN" or "BG-Test" may be used when working with manual feed on table milling machines. Furthermore, for safety reasons, the speed range specified on the tool must not be exceeded or fallen short of. The tools for manual feed may only be used when running against the feed.

Advantageous for good cutting results is the use of tools with high concentricity and balance quality, which is achieved by using centring interfaces such as hydro clamping systems, HSK holders or shrinking systems.

Tool examples:



DP-jointing cutter WhisperCut

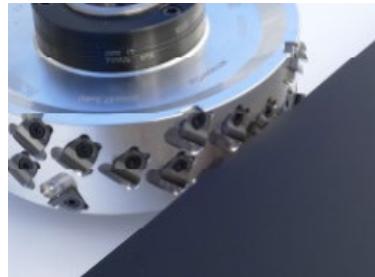

DP-WhisperCut EdgeExpert



DP-jointing cutter with fixed tipping



DP-jointing cutter EdgeExpert

The application parameters of the jointing cutters should be selected so that the tooth feed ( $f_z$ ) is between 0.25 and 0.65 mm.

# Machining recommendation

## Duropal XTreme

| Dimensions<br>DxSxBo<br>[mm] | RPM n<br>[min <sup>-1</sup> ] | No. of<br>teeth<br>Z | Feed<br>speed v <sub>f</sub><br>[m/min] | ID                     |                        |                        | Machine                      |
|------------------------------|-------------------------------|----------------------|---|------------------------|------------------------|------------------------|------------------------------|
|                              |                               |                      |   | HW<br>Turnblades       | WhisperCut<br>DP       | Fixed cut-<br>ters DP  |                              |
| 100x56x30<br>100x43x30       | 12,000                        | 3                    | 10 - 18                                 | LH 024692<br>RH 024691 | LH 090885<br>RH 090886 |                        | Brandt, IMA, Stefani,<br>SCM |
| 125x43x30                    | 9,000                         | 3                    | 10 - 15                                 | LH 024685<br>RH 024685 | LH 075627<br>RH 075627 |                        | HOMAG, Biesse                |
| 125x43x30                    | 9,000                         | 3                    | 10 - 15                                 |                        | LH 192094<br>RH 192095 |                        | IMA                          |
| 125x32x30                    | 9,000                         | 3                    | 10 - 15                                 |                        |                        | LH 192092<br>RH 192093 | IMA                          |
| 180x43x35                    | 6,000                         | 4                    | 15 - 20                                 |                        |                        | LH 090841<br>RH 090842 | IMA, HOMAG                   |
| 180x43x35                    | 6,000                         | 6                    | 15 - 20                                 |                        |                        | LH 192056<br>RH 192057 | IMA, HOMAG                   |
| 180x34x35                    | 6,000                         | 8                    | 20 - 25                                 |                        |                        | LH 192060<br>RH 192061 | IMA, HOMAG                   |
| 200x16-<br>30x35             | 6,000                         | 4                    | 10 - 15                                 |                        |                        | LH 192010<br>RH 192010 | KAL,<br>Double-end tenoner   |
| 200x16-<br>30x35             | 6,000                         | 6                    | 15 - 20                                 |                        |                        | LH 192011<br>RH 192011 | KAL,<br>Double-end tenoner   |
| 200x16-<br>30x35             | 6,000                         | 8                    | 20 - 25                                 |                        |                        | LH 192066<br>RH 192066 | KAL,<br>Double-end tenoner   |
| 200x16-<br>30x35             | 6,000                         | 10                   | 30 - 35                                 |                        |                        | LH 192108<br>RH 192109 | KAL,<br>Double-end tenoner   |

Other dimensions and numbers of teeth available on request

### For processing worktops with postforming edges

| Dimensions<br>DxSxBo<br>[mm] | RPM n<br>[min <sup>-1</sup> ] | No. of<br>teeth<br>Z | Feed<br>speed v <sub>f</sub><br>[m/min] | ID<br>WhisperCut       | Design          | Machine         |
|------------------------------|-------------------------------|----------------------|---|------------------------|-----------------|-----------------|
| 125x43x30                    | 9,000                         | 3                    | 10-15                                   | LH 192249<br>RH 192249 | EdgeExpert      | Biesse<br>Homag |
| 125x63x30                    | 9,000                         | 3                    | 10-15                                   | LH 192250<br>RH 192250 | EdgeExpert      | Biesse<br>Homag |
| 125x43x30                    | 9,000                         | 3                    | 10-15                                   | LH 192369<br>RH 192370 | EdgeExpert      | IMA             |
| 125x63x30                    | 9,000                         | 3                    | 10-15                                   | LH 192301<br>RH 192302 | EdgeExpert      | IMA             |
| 100x43x30                    | 9,000                         | 3                    | 10-15                                   | LH 192363<br>RH 192364 | EdgeExpert      | SCM             |
| 125x43x30                    | 9,000                         | 3                    | 10-15                                   | LH 192394<br>RH 192394 | PLUS EdgeExpert | Biesse, Homag   |
| 125x43x30                    | 9,000                         | 3                    | 10-15                                   | LH 192395<br>RH 192396 | PLUS EdgeExpert | IMA             |

Other dimensions and numbers of teeth available on request

# Machining recommendation

## Duropal XTreme

### Hoggers for throughfeed machines

Diamond compact hoggers, which generate little friction and cutting pressure, are recommended. The Leitz Diamaster DT Premium type mounted on a hydraulic clamping element is particularly suitable for maximum radial and axial runout and excellent machining quality and long tool life. The cutting speed ( $v_c$ ) is 80 m/s at the usual speed ( $n$ ) 6000 min<sup>-1</sup> and diameter (D) 250 mm. The application parameters and the number of teeth of the hoggers should be selected so that the tooth feed ( $f_z$ ) is between 0.12 - 0.18 mm.

| Dimensions<br>DxSBxBO<br>[mm] | RPM n<br>[min <sup>-1</sup> ] | No. of<br>teeth Z | Feed speed<br>$v_f$ [m/min] | ID, DT Premium mounted<br>on hydro clamping element<br>for spindle HF40 |               | Machine                                      |
|-------------------------------|-------------------------------|-------------------|-----------------------------|---|---------------|--|
|                               |                               |                   |                             | LH  | RH            |  |
| 250x10x60                     | 6,000                         | 24                | 30                          | <b>190382</b>   | <b>190383</b> | Edge banding machines,<br>double-end tenoner |
| 250x10x60                     | 6,000                         | 36                | 40                          | <b>190390</b>   | <b>190391</b> | Edge banding machines,<br>double-end tenoner |
| 250x10x60                     | 6,000                         | 48                | 50                          | <b>190398</b>   | <b>190399</b> | Edge banding machines,<br>double-end tenoner |
| 250x10x60                     | 6,000                         | 60                | 80                          | <b>190406</b>   | <b>190407</b> | Edge banding machines,<br>double-end tenoner |

Other dimensions available on request



Leitz DT Premium hogger

# Machining recommendation


## Duropal XTreme

### Edge processing on edge banding machines

Radii cutters and scrapers on edge banding machines must be set so that the tools do not touch the tool material. For panels with protective foil, the foil must not be damaged.


#### Radius cutter / bevel cutter

Radius cutters should have a profile run-out of at least 10°. The setting of the radius and bevel cutters must be selected so that there is only contact with the edge.

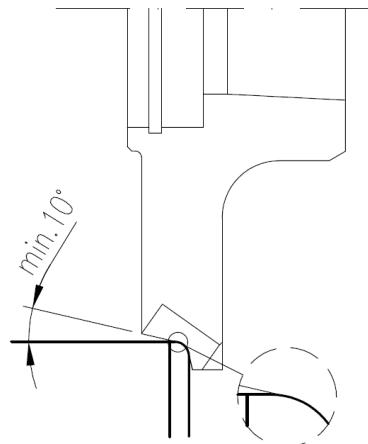


#### Profile scrapers

Profile scrapers are equipped with a profile relief and can easily be used for finishing the Duropal XTreme panels with exact adjustment. To avoid possible damage to the protective foil or decorative layer, scrapers with an enlarged profile run-out of up to 15° are recommended.

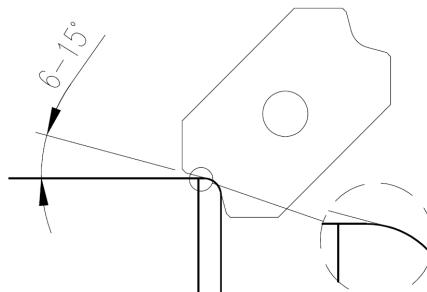

#### Flat scrapers

Flat scrapers should preferably have an inclination of 2 - 4° from the edge to the plate and should not touch the protective foil and decorative layer.

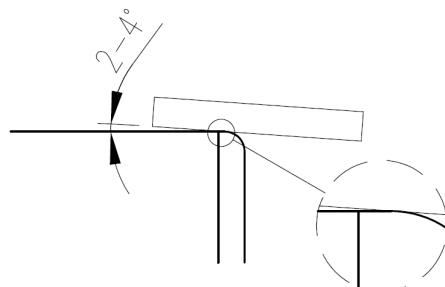

All dimensions available on request

# Machining recommendation

## Duropal XTreme

### Groove processing

For grooving, tools with a high number of teeth should preferably be selected for optimum edge quality. The tooth feed rate ( $f_z$ ) should be in the range of 0.03 - 0.06 mm when machining with feed (GLL).

### CNC Machining Centres

Spiral solid carbide cutters (VHW) or preferably diamond tipped (DP) routers are best suited for machining on router and machining centres.

In order to produce break-out-free edges on the top layers of the panel, DP routers with a spiral-shaped cutting arrangement with alternating shear angle are to be used. It is advantageous to use routers with an increased shear angle ( $>30^\circ$ ). When machining Duropal XTreme panels, it is particularly recommended to use the Leitz Diamaster EdgeExpert routers with a large shear angle of up to  $50^\circ$  for the best edge quality, such as for zero-joint edging.

Sizing tools with a higher number of teeth compared to standard tools generally tend to offer better cutting quality. Pre-milling of the workpieces is recommended to reduce tool wear during finish machining due to the low chip removal (between 0.5 to 2.0 mm).

Good workpiece clamping on the machine must be ensured. To support the vacuum suction devices, additional mechanical clamping elements can be used if necessary. We recommend stable and rigid Leitz ThermoGrip® shrink chucks for maximum concentricity and balance quality, for perfect cutting quality. A good machining result can only be achieved with sufficient rigidity of the machine, such as on gantry machines.



#### Recommended application data:

RPM  $n = 18,000 - 24,000 \text{ min}^{-1}$

#### Feed speed

$v_f = 8-10 \text{ (Z2) and } 14-18 \text{ (Z3) m}^{-1}$

$v_f = 20-24 \text{ (Z2 Nesting) m}^{-1}$

#### Tooth feed rate

$f_z = 0.15-0.25 \text{ mm}$

$f_z = 0.40-0.60 \text{ mm (Nesting)}$

# Machining recommendation

## Duropal XTreme

### Diamond tipped shank router cutters

| D<br>[mm] | NL<br>[mm] | S<br>[mm] | No. of<br>teeth<br>Z | Direction of<br>rotation | Version                      | ID     |
|-----------|------------|-----------|----------------------|--------------------------|------------------------------|--------|
| 16        | 28         | 20        | 2+2                  | RH                       | Diamaster PRO                | 191042 |
| 20        | 28         | 20        | 2+2                  | RH                       | Diamaster Quattro            | 091235 |
| 20        | 28         | 20        | 3+3                  | RH                       | Diamaster PLUS <sup>3</sup>  | 191051 |
| 12        | 24         | 12        | 2+2                  | RH                       | Diamaster PRO, Nesting       | 191060 |
| 20        | 32         | 20        | 2+2                  | RH                       | Diamaster Quattro EdgeExpert | 191071 |
| 20        | 48         | 25        | 2+2                  | RH                       | Diamaster Quattro EdgeExpert | 191072 |

Other dimensions available on request

### For the highest quality standards and for processing worktops with postforming edges

| D<br>[mm] | NL<br>[mm] | S<br>[mm] | No. of<br>teeth<br>Z | Direction of<br>rotation | Version                                | ID     |
|-----------|------------|-----------|----------------------|--------------------------|--|--------|
| 25        | 30         | 25        | 3+3                  | RH                       | Diamaster PLUS <sup>3</sup> EdgeExpert | 191073 |
| 25        | 35         | 25        | 3+3                  | RH                       | Diamaster PLUS <sup>3</sup> EdgeExpert | 191074 |
| 25        | 48         | 25        | 3+3                  | RH                       | Diamaster PLUS <sup>3</sup> EdgeExpert | 191075 |

Other dimensions available on request



Machining examples

# Machining recommendation

## Duropal XTreme

### Bohren

Boreholes tend to flare and fray slightly due to the surface finish of the coating. In principle, therefore, only sharp drills with a cutting edge geometry should be used.

Drilling on the opposite side is possible without tearing. For drilling, carbide-tipped or preferably twist, dowel hole and hinge boring bits made of solid carbide (VHM) are recommended.

On CNC machining centres, it is advisable to use the drills in the main spindle instead of in the drilling beam, due to the higher stability and the possibility of drilling at higher speeds.

#### Dowel drills

|                                   |               |
|-----------------------------------|---------------|
| RPM n [min <sup>-1</sup> ]        | 4,000 - 6,000 |
| Feed speed v <sub>f</sub> [m/min] | 0.5 - 2.0     |

#### Through-hole boring bits

|                                   |               |
|-----------------------------------|---------------|
| RPM n [min <sup>-1</sup> ]        | 4,000 - 6,000 |
| Feed speed v <sub>f</sub> [m/min] | 0.5 - 1.0     |

#### Hinge boring bits

|                                   |               |
|-----------------------------------|---------------|
| RPM n [min <sup>-1</sup> ]        | 3,000 - 4,500 |
| Feed speed v <sub>f</sub> [m/min] | 0.5 - 2.0     |

### Performance times

Tool performance times are influenced by a variety of factors, so that no performance time statements or rights can be derived within the scope of this machining guideline. The information on the tools and machining parameters are recommended guide values. Machine or process constellations can lead to deviating parameters. An optimal adaptation of machine, tool and material as well as customer-specific requirements can only be carried out on site together with a Leitz application engineer.

# Machining recommendation

## Duropal XTreme

### Explanation of abbreviations

|                      |  |                     |   |
|----------------------|--|---------------------|---|
| A                    | = dimension A  | LH                  | = left hand rotation                      |
| $a_c$                | = cutting thickness (radial)                               | M                   | = metric thread                           |
| $a_a$                | = cutting depth (axial)                                    | MBM                 | = minimum order quantity                  |
| ABM                  | = dimension  | MC                  | = multi-purpose steel, coated             |
| APL                  | = panel raising length                                     | MD                  | = thickness of knife                      |
| APT                  | = panel raising depth                                      | $\text{min}^{-1}$   | = revolutions per minute (RPM)            |
| AL                   | = working length   | MK                  | = morse taper                             |
| AM                   | = number of knives   | $\text{m min}^{-1}$ | = metres per minute                       |
| AS                   | = anti sound (low noise design)                            | $\text{m s}^{-1}$   | = metres per second                       |
| b                    | = overhang   | n                   | = RPM                                     |
| B                    | = width  | $n_{\text{max}}$    | = maximum permissible RPM                 |
| BDD                  | = thickness of shoulder                                    | NAL                 | = position of hub                         |
| BEM                  | = note   | ND                  | = thickness of hub                        |
| BEZ                  | = description  | NH                  | = zero height                             |
| BH                   | = tipping height   | NL                  | = cutting length                          |
| BO                   | = bore diameter  | NLA                 | = pinhole dimensions                      |
| CNC                  | = Computerized Numerical Control                           | NT                  | = grooving depth                          |
| d                    | = diameter   | P                   | = profile                                 |
| D                    | = cutting circle diameter                                  | POS                 | = cutter position                         |
| D0                   | = zero diameter  | PT                  | = profile depth                           |
| DA                   | = outside Diameter   | PG                  | = profile group                           |
| DB                   | = diameter of shoulder                                     | QAL                 | = cutting material quality                |
| DFC                  | = Dust Flow Control (optimised chip clearance)             | R                   | = radius                                  |
| DGL                  | = number of links  | RD                  | = right hand twist                        |
| DIK                  | = thickness  | RH                  | = right hand rotation                     |
| DKN                  | = double keyway  | RP                  | = radius of cutter                        |
| DP                   | = polycrystalline diamond                                  | S                   | = shank dimension                         |
| DRI                  | = rotation   | SB                  | = cutting width                           |
| FAB                  | = width of rebate  | SET                 | = set                                     |
| FAT                  | = depth of rebate  | SLB                 | = slotting width                          |
| FAW                  | = bevel angle  | SLL                 | = slotting length                         |
| FLD                  | = flange diameter  | SLT                 | = slotting depth                          |
| $f_z$                | = tooth feed   | SP                  | = tool steel                              |
| $f_{z_{\text{eff}}}$ | = effective tooth feed                                     | ST                  | = Cobalt-basis cast alloys, e.g. Stellit® |
| GEW                  | = thread   | STO                 | = shank tolerance                         |
| GL                   | = total length   | SW                  | = cutting angle                           |
| GS                   | = Plunging edge  | TD                  | = diameter of tool body                   |
| H                    | = height   | TDI                 | = thickness of tool                       |
| HC                   | = tungsten carbide, coated                                 | TG                  | = pitch                                   |
| HD                   | = wood thickness (thickness of workpiece)                  | TK                  | = reference diameter                      |
| HL                   | = high-alloyed tool steel                                  | UT                  | = cutting edges with irregular pitch      |
| HS                   | = high-speed steel (HSS)                                   | V                   | = number of spurs                         |
| HW                   | = tungsten carbide (TCT)                                   | $v_c$               | = cutting speed                           |
| ID                   | = ident number   | VE                  | = feed speed                              |
| IV                   | = insulation glazing                                       | VSB                 | = packing unit                            |
| KBZ                  | = abbreviation   | WSS                 | = adjustment range                        |
| KLH                  | = clamping height  | Z                   | = workpiece material                      |
| KM                   | = edge breaker   | ZA                  | = number of teeth                         |
| KN                   | = single keyway  | ZF                  | = number of fingers                       |
| KNL                  | = combination pinhole consists of 2/7/42 2/9/46,35 2/10/60 | ZL                  | = tooth shape (cutting edge shape)        |
| L                    | = length   |                     |   |
| I                    | = clamping length  |                     |   |
| LD                   | = left hand twist  |                     |   |
| LEN                  | = Leitz standard profiles                                  |                     |   |
|                      |  |                     |   |

In this machining recommendation, corresponding parameters for optimum machining of the designated materials are presented. The information on tools and machining parameters are guideline values without any claim to completeness or general validity. Machine or process-related marginal conditions can lead to deviating application parameters. Individual adjustments may be necessary in individual cases. In particular, the respective manufacturer's information on the intended use of the machine, tool and material must be observed. No rights can be derived from this machining recommendation. For solutions to complex tasks, please contact our technical advisor.

The information is based on the current state of the art and has been prepared with particular care and to the best of our knowledge. Due to continuous technical development as well as new standards and laws, technical changes may occur.