

Duropal XTreme plus (XPSM)

Machining of Duropal XTreme plus

Introduction

When machining XPSM by sawing, milling, grooving and boring, ensure that suitable tools and machining parameters are selected. The wrong choice of tools and/or their operating conditions can lead to white breakage and flanging of the workpiece surface and melting potentially the transport protection film. This machining guideline provides recommendations for optimum machining of this panel material.

General machining guidelines

When machining XPSM panels, the reference values from the table for the selection of the cutting speed (v_c) and the tooth feed rate (fz) should be observed, depending on the machining method.

Machining method	Cutting speed v _c [m/s]
Sawing	60 - 90
Hogging	60 - 80
Cutting	50 - 70
Routing	10 - 35

Machining method	Tooth feed rate fz [mm]
Sawing	0.02 - 0.12
Hogging	0.12 - 0.18
Cutting	0.30 - 0.55
Routing	0.15 - 0.25



These parameters are in relation to the tool diameter (D), number of teeth (Z), RPM (n) and feed speed (v_f) used on the processing machine. By selecting the correct parameters from the table, you can expect a good machining result.

The following formulas apply to the calculation of cutting speed, tooth feed rate and feed speed:

v_c - Cutting speed [m/s]

 $v_c = D \cdot \pi \cdot n / 60 \cdot 1000$

D - Tool diameter [mm]

n – RPM of tool [min⁻¹]

fz - Tooth feed rate [mm]

 $f_z = v_f \cdot 1000 / n \cdot z$

v_f - Feed speed [m/min]

n – RPM of tool [min⁻¹]

z – Number of teeth



Duropal XTreme plus (XPSM)

v_f - Tooth feed rate [m/min-1]

 $v_f = f_z \cdot n \cdot z / 1000$

fz - Feed speed [mm]

n – RPM of tool [min⁻¹]

z - Number of teeth

Cutting material

Tools with carbide cutting edges (HW) and diamond cutting edges (DP diamond polycrystalline) can be used. The use of tools with diamond cutting edges (DP) is recommended if cutting volume.



Duropal XTreme plus (XPSM)

Cutting panels with circular sawblades


General note:

- Visible side upwards
- Make sure that the sawblade protrudes correctly (see table)
- Adjust RPM and number of teeth to feed speed
- The use of a scoring sawblade is recommended for precise cuts on the bottom side of the panel


Depending on the sawblade protrusion, the entry and exit angle and thus the quality of the cutting edge change. If the top cutting edge becomes rough, set the circular sawblade higher. If the cut on the bottom side is rough, the circular sawblade must be set lower. In this way the most favourable height setting must be determined.

The following sawblade protrusions (Ü) must be set for sizing and panel sizing saws, depending on the diameter (D):

Circular sawblade diameter D [mm]	Protrusions Ü [mm]
250	ca. 5 - 10
300	
350	ca. 8 - 12
400	
450	ca. 10 - 15

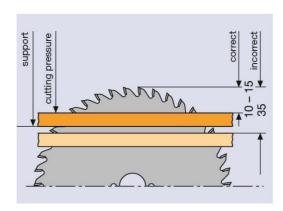

Circular sawblades with a high number of teeth are generally recommended for good machining surface quality. For circular sawing, the recommended cutting speed v_c is 60 - 80 m/s. For diamond-tipped circular sawblades, the cutting speed can be increased up to v_c 90 m/s.

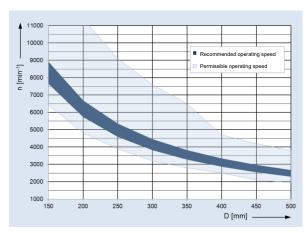


Speed diagram - depending on the circular sawblade diameter



Duropal XTreme plus (XPSM)

Recommended tooth shapes

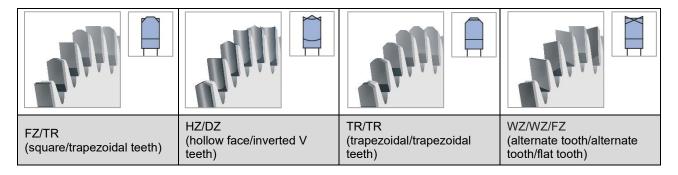

The tooth shapes FZ/TR and TR/TR are suitable for cutting to size. The WZ/FZ tooth form and HZ/DZ with special tooth geometry are suitable for sizing when higher quality requirements are placed on the cutting edge.

Sizing sawblades

Good cutting results and tool life are achieved with the saw tooth shape FZ/TR. With the tooth shapes WZ/FZ and HZ/DZ with special tooth geometry, excellent cutting results on the top layer are achieved, but a reduction in tool life must be expected.

Panel sizing sawblades

With tooth shape TR/TR, good cutting results and tool life are achieved. With tooth shape WZ/FZ with special tooth geometry, excellent cutting results for the surface layer are achieved, but a reduction in tool life must be expected.

CNC machining centres

The WZ/FZ tooth form with special tooth geometry achieves very good cutting results even in 5-axis applications on CNC machining centres.


Sizing saws and panel sizing saws with scoring unit and pressure beam

Scoring sawblades


For coated workpieces, the use of a scoring unit is recommended to achieve a good cutting edge quality on the tooth exit side. The cutting width of the scoring sawblade must be set slightly larger than that of the main circular sawblade so that the exiting tooth of the main saw can no longer touch the cutting edge. Since a secure, flat support of the workpieces is only guaranteed with pressure equipment, divided scoring circular sawblades are used on table and sizing saws.



Duropal XTreme plus (XPSM)



Panel sizing system with scoring unit and pressure device



Application diagram of conical scoring sawblade. When maintaining the tools (always in sets), the cutting widths must be matched to each other.

Circular sawblades for sizing saws and circular table saws (TC-tipped)

The following circular sawblades are suitable for cutting on table and sizing saws.

D [mm]	SB [mm]	TDI [mm]	BO [mm]	NLA	Z	ZF	sw °	ID
300	3.2	2.6	30	KNL	72	FZ/TR	5	165726
300	3.2	2.6	30	KNL	96	FZ/TR	5	165727
350	3.2	2.6	30	KNL	108	FZ/TR	5	165730
250	3.2	2.2	30	KNL	54	HZ/DZ	10	161300
303	3.2	2.2	30	KNL	68	HZ/DZ	10	161301
350	3.5	2.5	30	KNL	80	HZ/DZ	10	161302

Other dimensions available on request

Circular sawblades for panel sizing saws (TC-tipped)

The following RazorCut PLUS circular sawblades are suitable for cutting on panel sizing saws.

Machine	D [mm]	SB [mm]	TDI [mm]	BO [mm]	NLA	z	ZF	SW °	ID
	300	4.4	3.0	30	KNL	60	TR/TR	15	161137
Holz-Her, Mayer, Schelling	350	4.4	3.2	30	KNL + 2/13/94	72	TR/TR	15	161149
Homag	350	4.4	3.2	60	2/14/100	72	TR/TR	15	161150
Giben	350	4.4	3.2	75	-	72	TR/TR	15	161151
Selco	355	4.4	3.2	80	2/9/130 + 4/19/120	72	TR/TR	15	161153
Giben	380	4.4	3.2	50	4/13/80	72	TR/TR	15	161157
Homag	380	4.8	3.5	60	2/14/100 + 2/14/125	72	TR/TR	15	161159
SCM, Gabbiani,	400		0.0	0.0	2/14/110 + 2/7/110 +	70	TD /TD	4.5	404400
Selco	400	4.4	3.2	80	4/9/100 + 4/19/120 + 2/9/130	72	TR/TR	15	161163



Duropal XTreme plus (XPSM)

Machine	D [mm]	SB [mm]	TDI [mm]	BO [mm]	NLA	z	ZF	sw	ID
SCM, Gabbiani, Selco	430	4.4	3.2	80	2/14/110 + 2/7/110 + 4/9/100 + 4/19/120 + 2/9/130	72	TR/TR	15	161167
Mayer, Schelling	450	4.4	3.2	30	KNL + 2/13/94	72	TR/TR	15	161168
Homag	450	4.8	3.5	60	2/14/125 + 2/19/120	72	TR/TR	15	161169
Schelling	460	4.4	3.2	30	2/13/94	72	TR/TR	15	161170
SCM, Gabbiani, Selco	400	4.4	3.2	80	2/14/110 + 2/7/110 + 4/9/100 + 4/19/120 + 2/9/130	72	TR/TR	15	161163
SCM, Gabbiani, Selco	430	4.4	3.2	80	2/14/110 + 2/7/110 + 4/9/100 + 4/19/120 + 2/9/130	72	TR/TR	15	161167
Mayer, Schelling	450	4.4	3.2	30	KNL + 2/13/94	72	TR/TR	15	161168
Homag	450	4.8	3.5	60	2/14/125 + 2/19/120	72	TR/TR	15	161169
Schelling	460	4.4	3.2	30	2/13/94	72	TR/TR	15	161170
Vertical panel	355	3.0	2.2	30	KNL	120	WZ/FZ	10	161202
dividing saws,	400	3.2	2.5	30	KNL + 2/15/63	130	WZ/FZ	20	161206
without scoring unit	450	3.6	2.8	30	KNL + 2/15/63	140	WZ/FZ	20	161204


Other dimensions available on request

Panel sizing with circular sawblades is assumed as pre-machining. In order to create an optimal surface for edging and a breakout-free decorative edge, the saw cut must be reworked using a hogger or jointing cutter as described in the next chapter.

Circular saw blades for CNC machining centres

Circular saw blades for CNC machining centres										
Machine	D [mm]	SB [mm]	TDI [mm]	BO [mm]	NLA	Туре	z	ZF	sw	ID
Homag, Weeke	180	3.0	2.2	30	2/7/42 4/5.5/45 8/6/90	3 2 1	60	WZ/FZ	10	161250
Homag, IMA	200	3.0	2.2	30	2/7/42 4/6/52 8/6/90	3 2 1	65	WZ/FZ	10	161253
Biesse, Holz-Her	250	3.0	2.2	30	2/7/42 2/6/50 8/6/90	3 3 1	80	WZ/FZ	10	161259
Homag, Felder Format-4	280	3.0	2.2	30	2/7/42 8/6/90	3 1	85	WZ/FZ	10	161260
Biesse	300	3.0	2.2	50	1/6/80 6/5.5/80	3	100	WZ/FZ	10	161266
Homag	350	3.5	2.7	30	8/6/90	1	110	WZ/FZ	10	161263

Other dimensions and side holes available on request



Type 1: Countersunk to the right

Type 2: Countersunk to the left

Type 3: Secondary hole without countersink



Duropal XTreme plus (XPSM)

Jointing on throughfeed systems

Cutterheads with DIA turnblade knives or fixed cutterheads are generally suitable for machining XPSM panels. Jointing tools with alternating centre angles must be used to create tear-free edges on the top layers of the panel. The use of jointing cutters with a larger cutting angle (>30°) is advantageous, as they can also be used to process wide surfaces covered with protective film without any problems. Sizing tools with a higher number of teeth (Z) compared to standard tools tend to provide better cutting quality. Furthermore, ensure a low chip removal between 0.7 to 2.0 mm to reduce tool wear.

Only tools marked "MAN" or "BG-Test" may be used when working with manual feed on table milling machines. In addition, the speed range specified on the tool must not be exceeded or undercut for safety reasons. Tools for manual feed may only be used in counter-rotation.

For good cutting results, the use of tools with high concentricity and balance quality is recommended, this can be achieved by using centring interfaces such as hydro clamping systems, HSK holders or shrinking systems.

The application parameters of the jointing cutters should be selected so that the tooth feed (fz) is between 0.25 and 0.65 mm.

Tool examples:



DP-jointing cutter WhisperCut



DP-WhisperCut EdgeExpert



DP-jointing cutter EdgeExpert



Duropal XTreme plus (XPSM)

Dimensions DxSBxBO [mm]	RPM n [min ⁻¹]	No. of teeth Z	Feed speed v _f [m/min]	ID WhisperCut	Design	Machine
100x43x30	12,000	3	10-15	LH 090885 RH 090886	Standard	Brandt, IMA, Stefani, SCM
125x43x30	9,000	3	10-15	LH 075627 RH 075627	Standard	HOMAG, Biesse
125x43x30	9,000	3	10-15	LH 192094 RH 192095	Standard	IMA
125x63x30	9,000	3	10-15	LH 192096 RH 192097	Standard	IMA
125x43x30	9,000	3	10-15	LH 192249 RH 192249	EdgeExpert	Biesse Homag
125x63x30	9,000	3	10-15	LH 192250 RH 192250	EdgeExpert	Biesse Homag
125x43x30	9,000	3	10-15	LH 192369 RH 192370	EdgeExpert	IMA
125x63x30	9,000	3	10-15	LH 192301 RH 192302	EdgeExpert	IMA
100x43x30	9,000	3	10-15	LH 192363 RH 192364	EdgeExpert	SCM
125x43x30	9,000	3	10-15	LH 192394 RH 192394	PLUS EdgeExpert	Biesse, Homag
125x43x30	9,000	3	10-15	LH 192395 RH 192396	PLUS EdgeExpert	IMA

Other dimensions and numbers of teeth available on request



Duropal XTreme plus (XPSM)

Hoggers for throughfeed machines

Diamond compact hoggers, which generate little friction and cutting pressure, are recommended. The Leitz Diamaster DT Premium type mounted on a hydraulic clamping element is particularly suitable for maximum radial and axial runout and excellent machining quality and long tool life. The cutting speed (v_c) is 80 m/s at the usual speed (n) 6,000 min⁻¹ and diameter (D) 250 mm. The application parameters and the number of teeth of the hoggers should be selected so that the tooth feed (fz) is between 0.12 - 0.18 mm.

Dimensions	RPM n	No. of	Feed speed	II	D	Danism
DxSBxBO [mm]	[min ⁻¹]	teeth Z	v _f [m/min]	LH	RH	Design
250x10x60	6,000	35	35	190358	190359	Compact hogger
250x10x60	6,000	45	45	190360	190361	Compact hogger
250x10x60	6,000	55	55	190362	190363	Compact hogger
250x10x60	6,000	24	30	190382	190383	Compact hogger DT Premium
250x10x60	6,000	36	40	190390	190391	Compact hogger DT Premium
250x10x60	6,000	48	50	190398	190399	Compact hogger DT Premium
250x10x60	6,000	60	80	190406	190407	Compact hogger DT Premium

Other dimensions available on request



Leitz DT Premium hogger




Duropal XTreme plus (XPSM)

Edge processing on edge banding machines

Radii cutters and scrapers on edge banding machines must be set so that the tools do not touch the main panel material. For panels with protective foil, the foil must not be damaged.


Radii cutter / bevel cutter

Radii cutters should have a profile run-out of at least 10°. The setting of the radius and bevel cutters must be selected so that there is only contact with the edge.

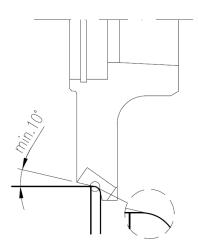


Profile scrapers

Profile scrapers are equipped with a profile relief and can easily be used for finishing the XPSM panels with exact adjustment. To avoid possible damage to the protective foil or decorative layer, scrapers with an enlarged profile run-out of up to 15° are recommended.



Flat scrapers

Flat scrapers should preferably have an inclination of 2 - 4° from the edge to the plate and should not touch the protective foil and decorative layer.



All dimensions available on request



Duropal XTreme plus (XPSM)

Groove processing

For grooving, tools with a high number of teeth should preferably be selected for optimum edge quality. The tooth feed rate (f_z) should be in the range of 0.03 - 0.06 mm when machining with feed (GLL).

CNC Machining Centres

Spiral solid carbide cutters (VHW) or preferably diamond tipped (DP) routers are best suited for machining on router and machining centres.

In order to produce break-out-free edges on the top layers of the panel, DP routers with a spiral-shaped cutting arrangement with alternating shear angle are to be used. It is advantageous to use routers with an increased shear angle (>30°). When machining XPSM panels, it is particularly recommended to use the Leitz Diamaster EdgeExpert routers with a large shear angle of up to 50° for the best edge quality, such as for zero-joint edging.

Sizing tools with a higher number of teeth compared to standard tools generally tend to offer better cutting quality. Pre-milling of the workpieces is recommended to reduce tool wear during finish machining due to the low chip removal (between 0.5 to 2.0 mm).

Good workpiece clamping on the machine must be ensured. To support the vacuum suction devices, additional mechanical clamping elements can be used if necessary. To achieve perfect cutting quality, stable and rigid Leitz ThermoGrip® shrink chucks are recommended for maximum concentricity and balancing quality. The NiRo chuck provides additional flexibility. A good machining result can only be achieved if the machine is sufficiently rigid, for example on portal machines.





Recommended application data:

RPM n = $18,000 - 24,000 \text{ min}^{-1}$

Feed speed $v_f = 8-10 (Z2) \text{ and } 14-18 (Z3) \text{ m}^{-1}$ $v_f = 20-24$ (Z2 Nesting) m⁻¹

Tooth feed rate $f_7 = 0.15 - 0.25 \text{ mm}$ $f_z = 0.40-0.60 \text{ mm (Nesting)}$



Duropal XTreme plus (XPSM)

D [mm]	NL [mm]	S [mm]	No. of teeth Z	Direction of rotation	Version	ID
16	28	20	2+2	RH	Diamaster PRO	191042
20	28	20	2+2	RH	Diamaster Quattro	091235
20	28	20	3+3	RH	Diamaster PLUS ³	191051
12	24	12	2+2	RH	Diamaster PRO, Nesting	191060
20	32	20	2+2	RH	Diamaster Quattro EdgeExpert	191071
20	48	25	2+2	RH	Diamaster Quattro EdgeExpert	191072
25	30	25	3+3	RH	Diamaster PLUS³ EdgeExpert	191073
25	35	25	3+3	RH	Diamaster PLUS ³ EdgeExpert	191074
25	48	25	3+3	RH	Diamaster PLUS ³ EdgeExpert	191075

Other dimensions available on request

For grooving, grooving saws optimised for CNC machining centres are suitable for the respective machining units. For optimum machining quality, synchronised use is recommended.

D [mm]	SB [mm]	BO [mm]	NLA	z	ZF	ID
100	3,5	30		35	WZ/WZ/FZ	166000
120	3,5	20	3/4.5/35	35	WZ/WZ/FZ	166002
120	3,5	35	4/6.3/50	35	WZ/WZ/FZ	166004
125	5	30	4/5.5/48	35	WZ/WZ/FZ	166007
200	5	30	4/5.5/52	60	WZ/WZ/FZ	166012

Other dimensions available on request



Duropal XTreme plus (XPSM)

Drilling

Due to the surface properties of the coating, drill holes tend to flare and micro-crack. In principle, therefore, only sharp drills with a cutting edge geometry should be used.

For drilling, carbide-tipped or preferably twist, dowel hole and hinge boring bits made of solid carbide (VHM) are recommended.

On CNC machining centres, it is advisable to use the drills in the main spindle instead of in the drilling beam or aggregate, due to the higher stability and the possibility of drilling at higher speeds.

For tear-free fitting holes, it is recommended that these are milled out circularly as a pocket (e.g. ID 042760)

D [mm]	GL [mm]	NL [mm]	S [mm]	Design	ID			
Row holes and bline	d holes							
3	57.5	16	10x36	HW solid Z2	RH 230610			
5	57.5	25	10x25	HW solid Z2	RH 230612			
8	57.5	25	10x25	HW solid Z2	RH 230617			
10	57.5	25	10x25	HW solid Z2	RH 230620			
Through holes								
5	57.5	25	10x25	shank 10 mm, HW solid	LH 034018 RH 034019			
8	57.5	25	10x25	shank 10 mm, HW solid	LH 034022 RH 034023			
Fogging holes								
15	54.5	-	8x30	Hinge boring bit with chip breakers	034660			
25	54.5	-	8x30	Hinge boring bit with chip breakers	034656			
35	54.5	-	8x30	Hinge boring bit with chip breakers	034659			



Duropal XTreme plus (XPSM)

Performance times

Tool performance times are influenced by a variety of factors, therefore no performance time statements or rights can be derived within the scope of this machining guideline. The information on the tools and machining parameters are recommended guide values. Machine or process constellations can lead to deviating parameters. An optimal adaptation of machine, tool and material as well as customer-specific requirements can only be carried out on site together with a Leitz application engineer.



Duropal XTreme plus (XPSM)

Explanation of abbreviations

A	= dimension A	LH	= left hand rotation
a。	cutting thickness (radial)	-	
a	= cutting depth (axial)	M	= metric thread
ABM	= dimension	MBM	 minimum order quantity
APL	= panel raising length	MC	 multi-purpose steel, coated
APT	= panel raising depth	MD	= thickness of knife
AL.	= working length	min ⁻¹	 revolutions per minute (RPM)
MA	= number of knives	MK	= morse taper
AS	= anti sound (low noise design)	m min ⁻¹	= metres per minute
	- unit ovario (ori riores design)	m s ⁻¹	= metres per second
)	= overhang	_	= RPM
3	= width	n	
BDD	= thickness of shoulder	n _{max} . NAL	 maximum permissible RPM
BEM	= note		= position of hub
BEZ	= description	ND	= thickness of hub
BH	= tipping height	NH	= zero height
30	= bore diameter	NL	= cutting length
		NLA	= pinhole dimensions
CNC	= Computerized Numerical Control	NT	= grooving depth
1	= diameter	P	= profile
5	= cutting circle diameter	POS	
The second second			
00	= zero diameter	PT	= profile depth
AC	= outside Diameter	PG	= profile group
OB	= diameter of shoulder		
DFC	 Dust Flow Control (optimised chip clearance) 	QAL	 cutting material quality
OGL	= number of links	_	
DIK	= thickness	R	= radius
DKN	= double keyway	RD	= right hand twist
OP.	= polycrystalline diamond	RH	= right hand rotation
DRI	= rotation	RP	= radius of cutter
AB	= width of rebate	S	= shank dimension
FAT	= depth of rebate	SB	= cutting width
AW	bevel angle	SET	= set
LD	= flange diameter	SLB	= slotting width
	= tooth feed	SLL	= slotting length
zoff	= effective tooth feed	SLT	= slotting depth
z off	- 511551115155	SP	= tool steel
SEW	= thread	ST	= Cobalt-basis cast alloys,
GL VV	(a) (b) (b) (c) (c) (c) (c) (c) (c)	31	
	- 101211011911	OTO	e.g. Stellit®
GS	= Plunging edge	STO	= shank tolerance
4	= height	SW	= cutting angle
HC	= height = tungsten carbide, coated	TD	= diameter of tool body
ID.	= wood thickness (thickness of workpiece)	TDI	= thickness of tool
4L	= high-alloyed tool steel	TG	= pitch
HS		TK	= reference diameter
HW	= high-speed steel (HSS) = tungsten carbide (TCT)	IIX	= releience diameter
	- Languion Gardiac (101)	UT	= cutting edges with irregular pitch
D	= ident number		All the result of the second section of the section of
V	 insulation glazing 	V	= number of spurs
		V _c	= cutting speed
(BZ	= abbreviation	V,	= feed speed
KLH	= clamping height	VE	= packing unit
CM	= edge breaker	VSB	= adjustment range
(N	= single keyway	CONTRACTOR OF	POLICE CONTRACTOR CONT
KNL	= combination pinhole consists of	WSS	= workpiece material
	2/7/42 2/9/46,35 2/10/60	Asserta	- nomproce material
	The state of the s	Z	= number of teeth
L	= length	ZA	= number of fingers
	= clamping length	ZF	= tooth shape (cutting edge shape)
LD	= left hand twist	ZL	= finger length
LU .			

In this machining recommendation, corresponding parameters for optimum machining of the designated materials are presented. The information on tools and machining parameters are guideline values without any claim to completeness or general validity. Machine or process-related marginal conditions can lead to deviating application parameters. Individual adjustments may be necessary in individual cases. In particular, the respective manufacturer's information on the intended use of the machine, tool and material must be observed. No rights can be derived from this machining recommendation. For solutions to complex tasks, please contact our technical advisor.

The information is based on the current state of the art and has been prepared with particular care and to the best of our knowledge. Due to continuous technical development as well as